



## Original Research Article

# Comparative investigations of synthesis TiO<sub>2</sub> Nano-Particles from four different types of alcohols by Sol-Gel method and evaluation of their antibacterial activity

Mariam Farag Ambarak<sup>a,\*</sup> , Fawzia Muftah Aljazwia<sup>b</sup>, Randa Fawzi Alsupikhe<sup>a</sup>

<sup>a</sup> Department of Chemistry, Faculty of Science, University of Benghazi, Benghazi, Libya

<sup>b</sup> Department of Botany, Faculty of Science, University of Benghazi, Benghazi, Libya

### ARTICLE INFORMATION

Received: 12 April 2019

Received in revised: 21 May 2019

Accepted: 26 May 2019

Available online: 26 June 2019

DOI: [10.48309/JMNC.2019.4.7](https://doi.org/10.48309/JMNC.2019.4.7)

### KEYWORDS

TiO<sub>2</sub> nanoparticles

Synthesis

Sol-Gel method


Alchols

Antibacterial study

### ABSTRACT

TiO<sub>2</sub> nanoparticles were synthesized using a simple reaction of TiCl<sub>4</sub> with different types of primary and secondary alcohols. Four different alcohols (ethanol, isopropyl, isobutyl, and isobentyl alcohol) were investigated. The experiments were carried out to compare the products of the reactions with different precursors. The gelatine products were calcined at 400 °C and at 1000 °C in a box furnace and the effect of calcination temperature on the feature of nano-particles was studied. The synthesized TiO<sub>2</sub> nanoparticles were characterized using X-ray diffraction (XRD) and scanning electron microscopy (SEM). The results revealed that the average particle size was 8.9-18.4 nm. The antibacterial result of titanium dioxide nanoparticles at four types of bacteria was two gram-positive (*Staphylococcus aureus* and *Streptococcus sp.*) and two gram-negative (*Escherichia coli* and *Klebsiella sp.*). Also, nanoparticles titanium dioxide did not have any effect on these types of bacteria. The sol-gel method could be used for applications that involve nano-crystalline TiO<sub>2</sub> with anatase phase with low cost and simple preparation.

## Graphical Abstract

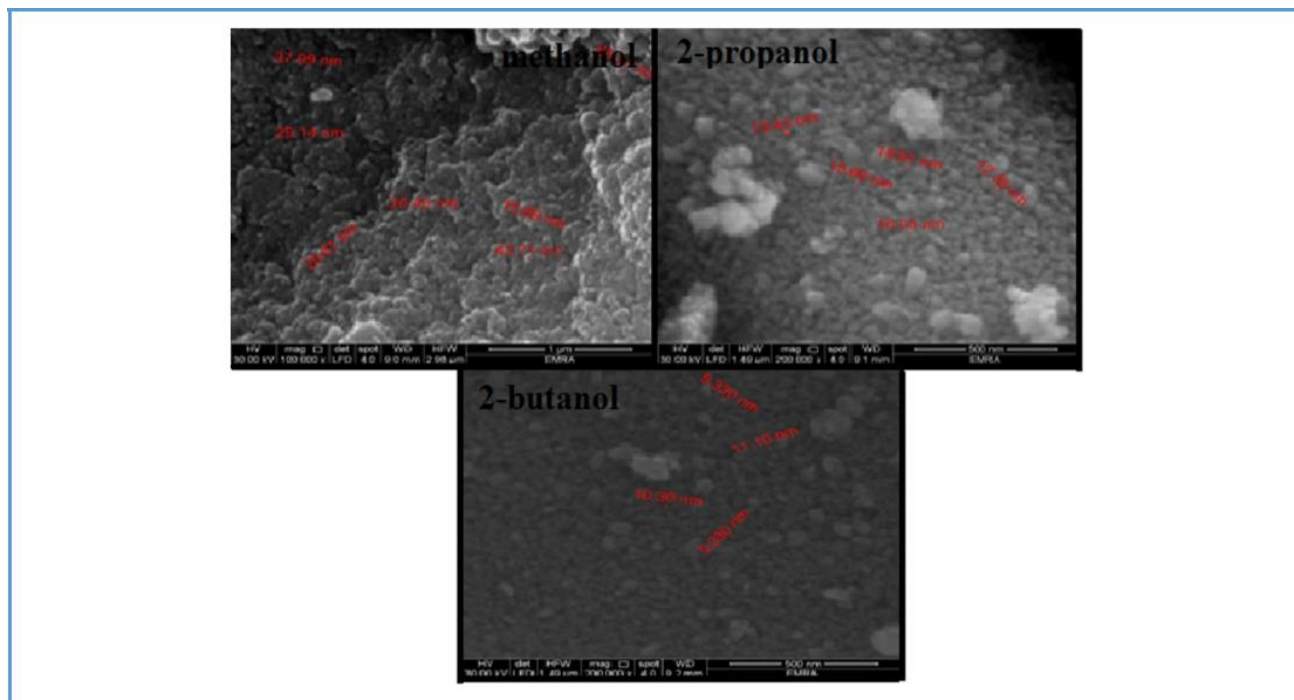

## Introduction

Nanotechnology is the control of matter at dimensions between nearly to 1-100 nm [1]. Nanoparticles have been studied in recent years as their potentials in catalysis, mechanical, optical, and electronic devices [2]. Titanium dioxide (TiO<sub>2</sub>) nanoparticles show high surface area per unit absorption of ultraviolet light in toners and coating materials [3]. Furthermore, titanium dioxide is used as semiconductor in wide range of applications such as photosensor, photocatalysis, dyes sensitized solar cells, optical filters, photovoltaic devices, UV light sensor, and biomedical applications [4]. Metal and metal oxide nanoparticles have been synthesized using various chemical and physical methods. Some of the commonly used synthetic methods are non-sputtering, solvothermal, reduction, electrochemical technique, and sol-gel technique [5]. Sol-gel method is an hydrolysis and poly-

condensation processes which forms a solid coating. This technique requires low temperature and is a manageable final product process [6, 7]. Alcohols and benzene are commonly used in this method [8]. In this work, the most popular methods for oxides preparation in Sol-Gel method were used to synthesize TiO<sub>2</sub> nanoparticles. The advantages of sol-gel method include molecular homogeneity, probability of use a big variation of precursors, microstructural and properties control, low purity conditions, simplicity of use at moderately low temperatures and low costs.

## Experimental Technique


### Materials and methods

Titanium tetrachloride TiCl<sub>4</sub> (99.99%, BDH, England), absolute ethanol (99.99%), isopropyl alcohol (99.99%), isobutyl alcohol (99.99%), and isobentyl alcohol (99.99%) were used in this study.

### Synthesis of $TiO_2$ nanoparticles

In synthesis of  $TiO_2$  nanoparticles by sol-gel method,  $TiCl_4$  was used as the precursor. 10 mL of  $TiCl_4$  was added to 250 mL well dried conical flask. After that, 100 mL of choosing alcohol was added from a burette, the reaction was set up in a fume hood. Addition of alcohol was dropped by the drop at constant stirring to obtain more homogenous nanoparticles. The alcohols were ethanol ( $C_2H_5OH$ ), isopropyl ( $C_3H_7OH$ ) and isobutyl ( $C_4H_9OH$ ) alcohol. A pale yellow solution was obtained with gelatinized precipitates with ethanol,

isopropyl alcohol and isobutyl alcohol reactions. Whereas isobutyl alcohol produces a black oily liquid with a bad smelling, pH of the solution was 1.5 and the weight of gelatines was about 20 gr [Figure 1](#) shows the  $TiO_2$  nanoparticles gels prepared from methanol, 2-propanol and 2-Butanol. then the Sol-Gels were vaporized at  $80^\circ C$  until dry gels were obtained. The three dry gels from (Ethanol, isopropyl and isobutyl alcohol) were calcined for one and a half in the box furnace at  $400^\circ C$  and  $1000^\circ C$  to get titanium dioxide nano powders.

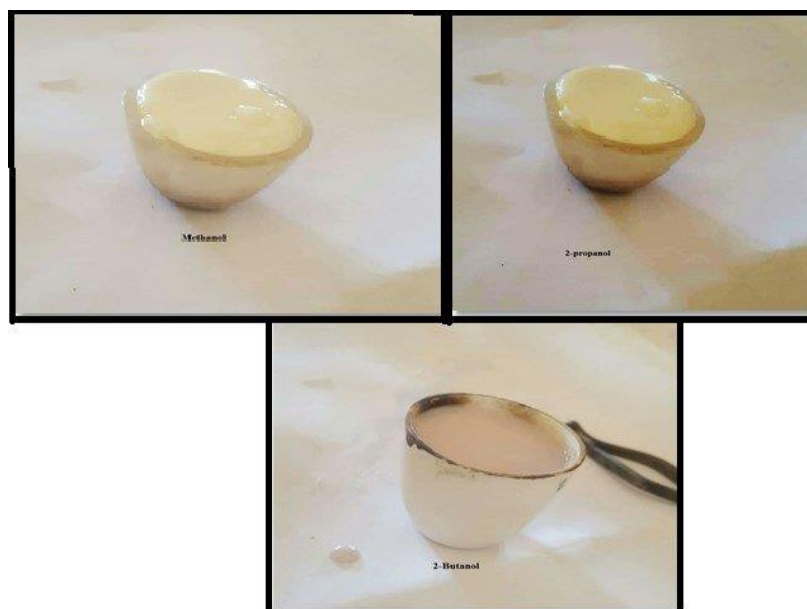

**Figure 1.**  $TiO_2$  nanoparticles Gels prepared from methanol, 2-Propanol, 2-Butanol

### Characterization of $TiO_2$ nanoparticles

X-ray diffraction (XRD-5500 2kw type), shows the crystallinity shape of the synthesized nanoparticles at room temperature. Scanning Electron Microscopy (SEM, Tescan VEGA2 SB) have been used to identify the morphological (size and shape) of the  $TiO_2$  nanoparticles that prepared in different types of alcohols.

### Result and Discussion

Titanium tetrachloride reacts with compounds containing active hydrogen atoms with loss of HCl. The replacement of chloride is usually unfinished in the non-appearance of an HCl acceptor like amine or alkoxide ion. The alkoxides are solids or liquids that can be distilled or sublimed such as Titanium isopropoxide (TIP) in chemical structure ( $C_{12}H_{28}O_4Ti$ ) and tetra-n-butyl orthotitanate

(TNB) in chemical structure ( $C_{16}H_{36}O_4Ti$ ). They are extremely hydrolysed by even traces of water, to give polymeric species with -OH- or -O- bridges. Even though monomeric types can exist, for example, when made from secondary and tertiary alcohols, and in dilute solution, alkoxides are usually polymers. Solid  $Ti(OC_2H_5)_4$  is a tetramer (with tetrahedral geometrical structure) that hydrolysis subsequently to  $TiO_2$  [9].

### X-ray diffraction (XRD) analysis

Figure 1 presents the X-ray diffraction pattern, SQD concentration (signal Quality Detector) and S-Q for  $TiO_2$  Nano powders prepared in methanol, isopropanol and isobutyl alcohol that calcined at  $400^\circ C$ . S-Q shown that, the purity of the samples was 100%, and  $TiO_2$  was anatase with tetragonal geometry shape has molar mass  $77.96\text{ g/mol}$  the SQD shown the sample consist of 40.1% oxygen and 59.9% titanium elements.

Crystalline sizes of  $TiO_2$  have been obtained by Scherrer's formula given by equation [10] (1):

$$D = \frac{K\lambda}{\cos\theta} \Delta(2\theta)$$

At which K is a constant that depend on the crystallite shape (0.9, with the supposition of sphere-shaped particles),  $\lambda$  is the X-ray wavelength, is the full width at half maximum of the selected peak and is the Bragg's angle of diffraction for the peak [11].

The XRD pattern results the sizes of Nanoparticles were identified at 2 values  $25.4^\circ, 37.2^\circ, 48.2^\circ, 54.3^\circ, 55.2^\circ$  matches to the crystal planes of (101), (004), (200), (105) agreement with the standard X-ray diffraction pattern (JCPDS files No 21-1272). The sizes of  $TiO_2$  nanoparticles have been calculated from Scherrer's equation, it was 11.55, 8.97, 13.90, 10.85 and 18.54 nm for all  $TiO_2$  prepared from different alcohols. There is no different in the size or the shape for  $TiO_2$  whatever the kind of alcohols that prepared from. The difference observed in the speed of reaction whereas the small mass alcohols shows faster reaction comparing to heavy mass alcohols, also there are differences in the colours of the produced Gels, it was white Gel with methanol, yellowed white Gel with isopropanol and pale grey to white with isobutyl alcohol. With Bentlyl alcohol ( $C_5H_{11}O$ ) we suppose the crowded on Titanium atom prevented to producing a  $TiO_2$  gel.

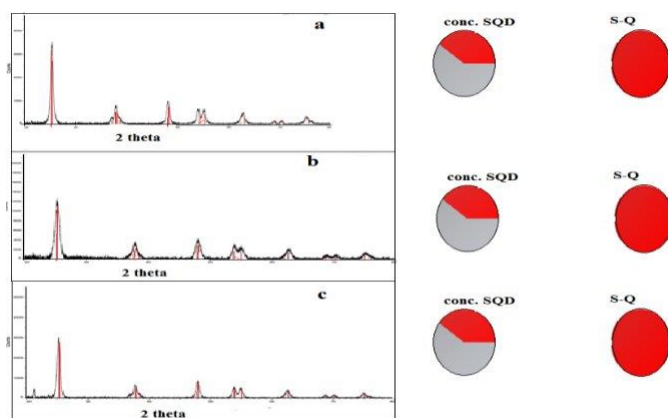


Figure 2. The XRD pattern, a) SQD conc., S-Q for  $TiO_2$  nanoparticles prepared, b) methanol, and c) isopropanol, isobutyl alcohol calcined at  $400^\circ C$


**Table 1.** Crystal sizes of TiO<sub>2</sub> nanoparticles prepared from different type of alcohols and calcined at 400 °C

Alcohol type	Phase of obtained TiO <sub>2</sub>	2θ (DEG)	D value	Grain size (nm)
Methanol (COD 1526931)	100% Anatase	25.412°	3.501	11.54
		37.209°	2.414	8.95
		38.143°	2.357	11.80
		54.334°	1.885	17.54
		25.304°	3.516	14.97
Isopropanol (COD 9009086)	100% Anatase	36.949°	2.430	17.32
		37.793°	2.332	8.97
		48.837°	1.892	13.98
		25.271	3.521	10.98
		37.699	2.384	9.87
Isobutyl alcohol (COD 5000223)	100% Anatase	38.509	2.335	14.99
		47.980	1.894	17.32

### Scanning electron microscope (SEM)

The SEM images in [Figure 3](#) show that, the TiO<sub>2</sub> gels have a crudely randomly shapes with sizes around the range 15 nm. After the thermal treatment for obtain TiO<sub>2</sub> powders and release the H<sub>2</sub>O particles the shapes tend to be more homogeneous spherical spongy phase. [Figure 4](#) shows the effect of temperature on shapes and sizes of TiO<sub>2</sub> powder at 400 °C.

From the [Figure 4](#) when the temperature increase the size of TiO<sub>2</sub> decreased and the shapes become more homogenous. But at 1000 °C the condition changes the particles tend to accumulate and stick together so that the agglomeration becomes apparent, as shown in [Figure 5](#). These results are in agreement with the data were reported by Haider A J [11].

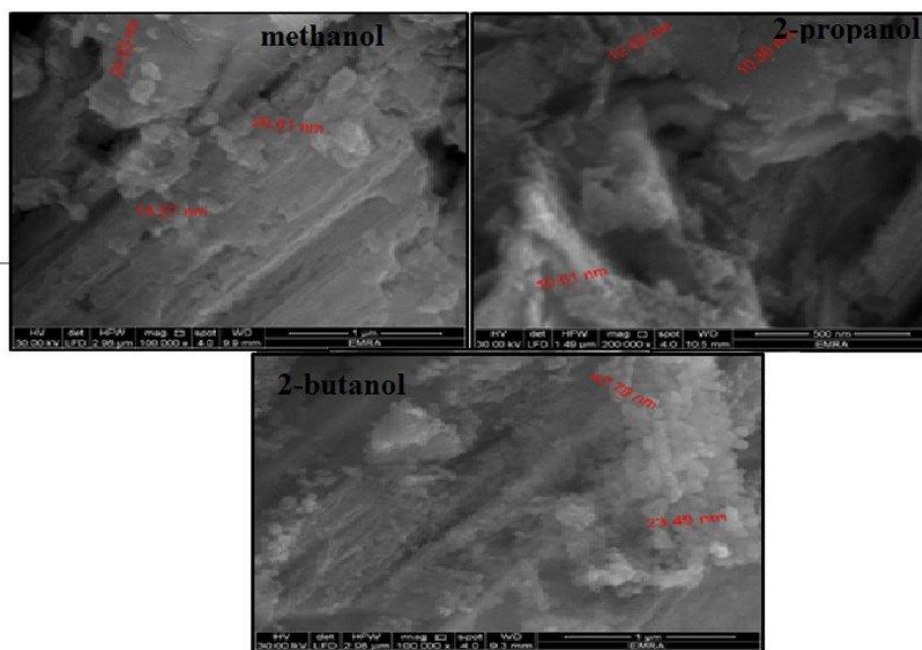

**Figure 3.** SEM images for TiO<sub>2</sub> nanoparticles Gel prepared by a) methanol b) Isopropanol, and c) Isobutyl alcohol

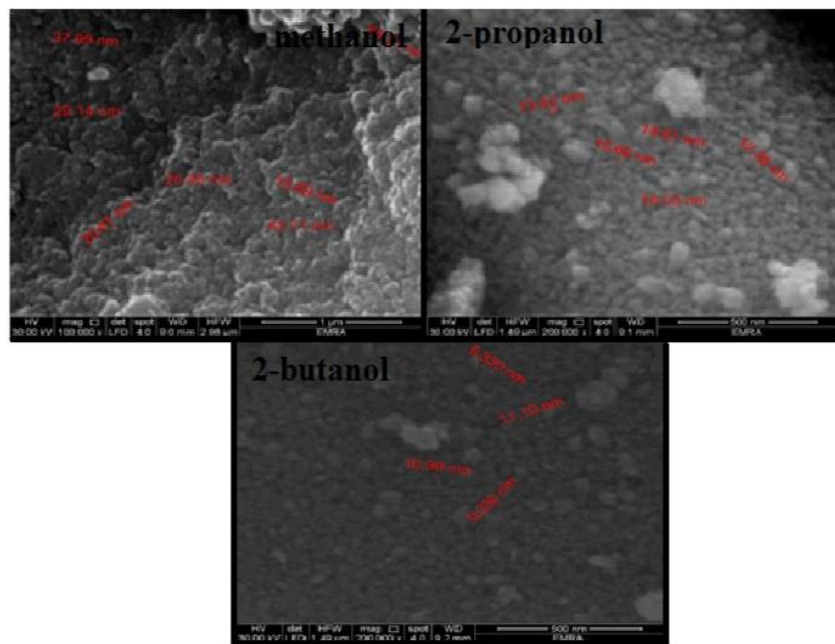


Figure 4. SEM images for TiO<sub>2</sub> nano powders calcined at 400 °C prepared by a) methanol, b) isopropanol, and c) isobutyl alcohol

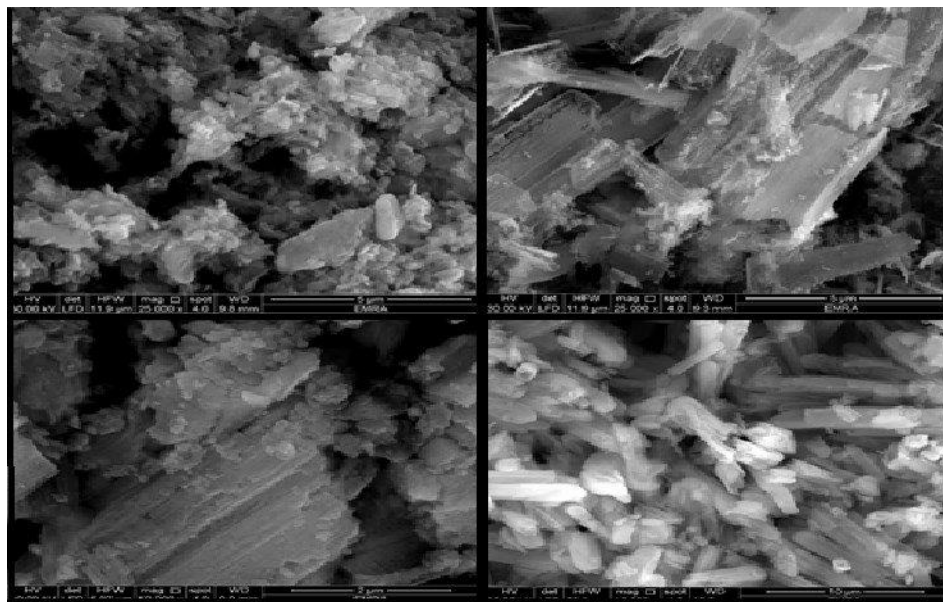


Figure 5. SEM images of TiO<sub>2</sub> nano powders calcined at 1000 °C prepared from a) methanol, b) isopropanol, and c) isobutyl alcohol

*Test microorganism*

Four clinical isolates of bacteria were used for the study: two gram-positive (*Staphylococcus aureus* and *Streptococcus sp.*)

and two gram-negative (*Escherichia coli* and *Klebsiella sp.*) bacteria were used to evaluate the antibacterial activity of titanium dioxide nanoparticles (TiO<sub>2</sub> NPs).

### Preparations of different concentration titanium dioxide nanoparticles

Suspensions of TiO<sub>2</sub> NPs with concentrations (50, 200, and 800 µg/mL) were prepared by suspending them in distilled water.

### Evaluation of antibacterial activity


Antibacterial activities of the different concentrations of TiO<sub>2</sub> NPs were evaluated using well diffusion method on Mueller-Hinton agar (Jahangirian *et al.*, 2013). Media was poured on two replicates petriplates of each species bacteria. After the media is solidified the four wells (7 mm diameter) were made in each plate and 100 µl of the different concentrations of TiO<sub>2</sub> nanoparticles (50, 200, and 800 µg/mL) and 100 µl of sterilized distilled water (negative

control) were added in these wells. Also, the bacteria were added to media at 37 °C. After 24 hours of incubation, each plate was examined and measured for the diameters of the zones of complete inhibition including the diameter of the wells.

## Results and discussion

### Antibacterial activity

In this study, results were obtained for the different concentration of synthesized nanoparticles tested (TiO<sub>2</sub> NPs, 50, 200 and 800 µg/mL) against four bacteria are presented in Figure 6. According to Figure 6 showed no effect of any bacteria treated with the different concentration of TiO<sub>2</sub> nanoparticles.

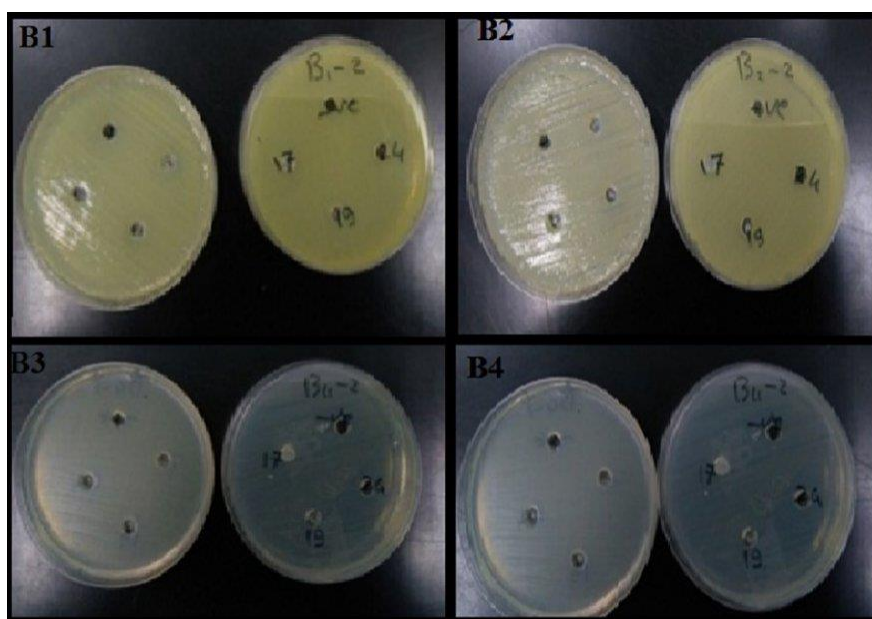

**Figure 6.** Effect of the different concentrations of of TiO<sub>2</sub> NPs (17= 800 µg/mL, 19= 200 µg/mL and 24=50 µg/mL) and sterilized distilled water (-ve= negative control) on B1) *Escherichia coli*, B2) *Klebsiella sp*, B3) *Staphylococcus aureus*, and B4) *Streptococcus sp*

The reason for emergence of bacterial resistance to TiO<sub>2</sub> is due to the structural composition of bacteria and preparation of TiO<sub>2</sub> which makes it difficult for TiO<sub>2</sub> to penetrate. We suggest that these particles are probably not

transferred from the exposure suspension to bacteria. Our results are not similar with another report using TiO<sub>2</sub> nanoparticles that showed the antibacterial effect on gram-positive and gram-negative bacteria [12–15].

## Conclusion

The morphological and optical properties of the titanium dioxide nanoparticles were found not affected by the type of alcohol that prepared from. There are no difference in quality and the properties of producing TiO<sub>2</sub> nanoparticles. The calcination temperature was studied at 400 °C and 1000 °C. The SEM results revealed that as the calcination temperature increase, the accumulation and the crystal size increased. The antibacterial result improved the TiO<sub>2</sub> do not have any effect as antibiotic.

## Acknowledgment

The authors would like to thank the University of Benghazi, Department of Chemistry, furthermore gratitude to the Arab-centre for Nanotechnology (Egypt) for help to complete this work.

## Disclosure statement

No potential conflict of interest was reported by the authors.

## Orcid

Mariam Farag Ambarak  0000-0002-2888-6590

## References

- [1]. Wolfgang G.K., Semmler-Behnke M., Qasim Ch. *Nano Today*, 2010, **5**:165
- [2]. Baolin H., Juei J.T., Kong Y.L., Hanfan Liu. *Journal of Molecular Catalysis A: Chemical*, 2004, **221**:121
- [3]. Hee Dong J., Kim Seong-Kil. *Materials Research Bulletin*, 2001, **36**:627
- [4]. Sara M., Askari M., Sasani Ghamsari M. *Journal of Materials Processing Technology*, 2007, **189**:296
- [5]. Sundrarajan M., Gowri S. *Chalcogenide Lett*, 2011, **8**:447
- [6]. Samira B., Kamyar Sh., Bee Abd Hamid Sh. *Journal of Chemistry* 2013, 2013:5 pages
- [7]. Sara M., Askari M., Sasani Ghamsari M. *Journal of Materials Processing Technology*, 2007, **189**: 296
- [8]. Mahmoud B., Masoud M., Sahar E. *Journal of Theoretical and Applied Physics*, 2017, **11**:79
- [9]. Surhayani Jefri SN., Abdullah A.H., Mohammad E.N. *Asian Journal of Green Chemistry*, 2019, **3**:271
- [10]. Azaroff L.V., Elements of X-Ray Crystallography, McGraw-Hill, New York, 1968, 552
- [11]. Haider A.J., AL-Anbari R.H., Khadim G.R. *TMREES*, 2017, **119**:332
- [12]. Sirimahachai U., Phongpaichit S., Wongnawa S. *Songklanakarinn J Sci Technol.*, 2009, **31**:517
- [13]. Bonnet M., Massard C., Philippe V., Camares O., Awitor K.O. *J. Biomater. Nanobiotechnol.*, 2015, **6**: 213
- [14]. Jahangirian H., Haron M. J., Ismail M. H. S., Rafiee-Moghaddam R., Afsah-Hejri L., Abdollahi Y., Rezayi M., Vafaei N. *Digest J. Nanomater. Biostru.*, 2013, **8**:1263
- [15]. Mahdy S.A., Mohammed W.H., Emad H., Abdul Kareem H., Shamel R., Mahdi S. *Journal of Babylon University/Pure and Applied Sciences/* 2017, **25**:955

**How to cite this manuscript:** Mariam Farag Ambarak\*, Fawzia Muftah Aljazwia, Randa Alsupikhe. Comparative investigations of synthesis TiO<sub>2</sub> nano-particles from four different types of alcohols by sol-gel method and evaluation of their antibacterial activity. *Journal of Medicinal and Nanomaterials Chemistry*, 2019, 1(4), 431-438  
.DOI: [10.48309/JMNC.2019.4.7](https://doi.org/10.48309/JMNC.2019.4.7)